

SAFETY GLASSES



GLASS UNLIMITED

TOUGHENED AND LAMINATED

|                                                       |    |
|-------------------------------------------------------|----|
| 1. Introduction                                       | 3  |
| 2. Laminated glass                                    | 4  |
| 3. Thermally toughened glass                          | 6  |
| 4. European classification standards                  | 7  |
| 5. EN 12600 – impact resistance                       | 8  |
| 6. EN 356 – burglar resistance                        | 10 |
| 7. EN 1063 – bullet resistance                        | 12 |
| 8. National regulations and safety-glass applications | 15 |
| 9. Availability                                       | 18 |
| 10. Installation instructions                         | 18 |
| 11. Maintenance, storage, handling and processing     | 18 |


## NB

*This brochure gives a general overview of the technical characteristics of AGC Flat Glass Europe's toughened and laminated safety glasses. It is the responsibility of users – not of AGC Flat Glass Europe – to satisfy themselves that a particular product is suitable for the proposed application and that the product itself, its application and the standards, regulations and codes of good practice in force in the relevant country or countries are satisfactory.*


*The proposed conditions under which a product is to be used should be verified by AGC Flat Glass Europe, its local representative or a glass specialist. Unless otherwise stipulated in advance and in writing, AGC Flat Glass Europe shall not be liable in any way for consequences arising from the use of a glass as illustrated in the examples in this brochure.*

*Not all products are available in all countries. For further information, consult your local AGC Flat Glass Europe representative.*

Glass is a recurrent feature of modern architecture: clear, reflective, insulating, solar control, coloured, textured ... glass can be processed in many ways to meet architects' and designers' requirements. The wide range available from AGC Flat Glass Europe combines technical and aesthetic features seamlessly. Naturally, safety is an integral consideration. A glass surface should be made secure enough to prevent both burglary and injury, should someone fall on it. This brochure also sets out the various safety requirements. There is a product and safety solution for every scenario. This brochure is designed to be an informative aid to anyone wishing to check the application of standards, safety classes and technical solutions in respect of a particular range. Be it laminated or toughened glass, AGC Flat Glass Europe has unrivalled expertise from which we would like both industrial players and those in the glass sector to benefit.

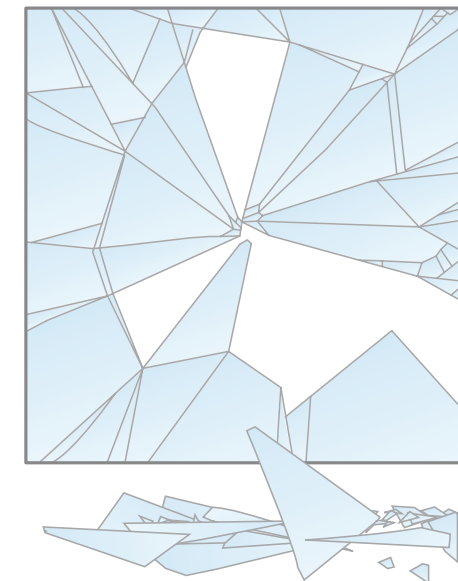

Float fragmentation

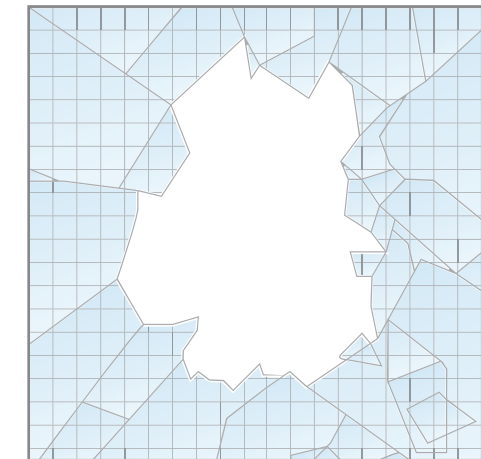

Safety glass fragmentation

This brochure supplements document 'Stratobel®/Stratophone®' and comprises the following:


- an overview of laminated and toughened glasses;
- a description of the various standards and tests used to classify safety glass and the corresponding AGC ranges;
- some examples of safety-glass applications.

## 2. LAMINATED GLASS

### 2.1. Description

A laminated glass is an assembly comprising at least two panes of glass bonded together across their entire surface by one or more interlayers. For laminated safety glasses, the most widely used interlayer is a PVB (polyvinyl butyral) film. In the event of breakage, the bond between the glass and the interlayer ensures that the broken pieces of glass remain in place (at least for a certain time or up to a specified load level).

In some cases, polycarbonate sheets may also be included.

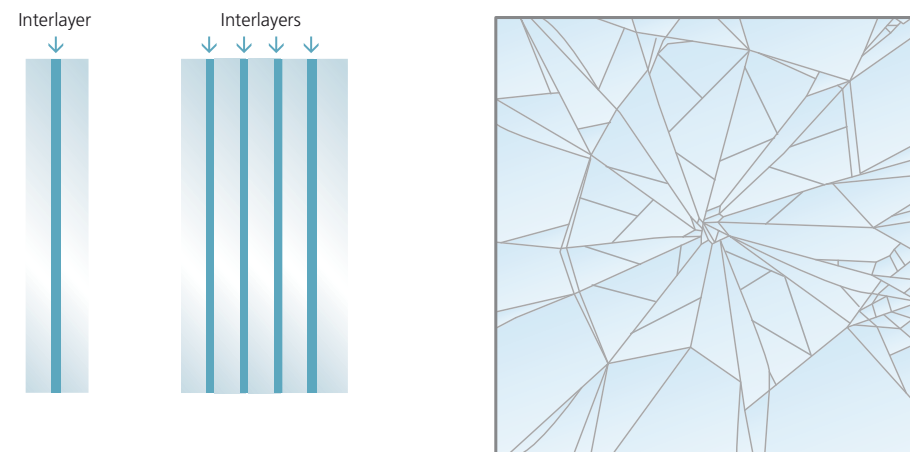

*Break pattern of laminated glass*

AGC has two ranges of laminated glass:

- Stratobel: laminated safety glass
- Stratophone: acoustic laminated safety glass

### 2.2. System

Laminated glasses with PVB interlayers have their own system to denote composition. This takes the form of two (or more) figures indicating the thickness of the different panes of glass in mm, followed by a further figure separated from the rest by a dot giving the number (rather than the thickness) of the PVB films between each pane of glass. The PVB films are 0.38 mm thick.

*Example:* A glazing denoted as 66.2 has two panes of (float) glass measuring 6 mm separated by two PVB films each 0.38 mm thick; some countries also describe laminated glass by giving its total thickness, namely 12.76 in the case of 66.2.

### 2.3. Use

Depending on its composition, thickness, number of components, number of PVB films and other factors, various levels of protection are available to meet requirements in terms of:

- protecting individuals against the risk of injury by:
  - pieces of sharp, broken glass;
  - falling (defenestration);
- protecting goods and safety against burglary and vandalism of private homes, shops and offices; in this context the glazing should remain in place and prevent anyone or anything penetrating it;
- protection against firearms;
- protection against explosions.

In addition to providing protection in the broad sense, laminated glass is also the only solution for applications such as floors, steps, lift shafts, balustrades and so forth.



### 2.4. Certification

Stratobel and Stratophone laminated glasses comply with standards EN ISO 12543 and are considered laminated safety glasses under standard EN ISO 12543-2. They are CE-marked in accordance with standard EN 14449.


## 3. THERMALLY TOUGHENED GLASS

### 3.1. Description

Thermally toughened glass<sup>1</sup> (so-called as opposed to annealed glass) is a glass which has been treated to increase its resistance. The glass may also undergo what is known as 'heat-soak' treatment after toughening. We recommend heat-soaking for all toughened glasses measuring 6 mm and above and which are likely to experience regular temperature changes.

The characteristics of thermally toughened glasses are fundamentally different from those of the base products from which they are manufactured:

- they cannot be cut, sawn, perforated or processed after toughening since the toughening process causes significant stress on the glass; all cutting, holes and any edge treatment must therefore be performed before toughening.
- they have much higher levels of mechanical strength and impact resistance; characteristic resistance via bending of thermally toughened glass is 120 N/mm<sup>2</sup> as compared with 45 N/mm<sup>2</sup> for annealed glass.
- they have a higher level of resistance to thermal shock: they can resist differences in temperature of approximately 200°C while in annealed glass, breakage can occur under temperature differences of approximately 30°C; however, this value can vary considerably and depends on the quality of the edge processing among other factors.
- in the event of breakage, they fragment into blunt pieces which are smaller than annealed glass, thereby limiting the risk of injury; thermally toughened glass is therefore only considered as a safety glass where protection against injury from sharp fragments is required.

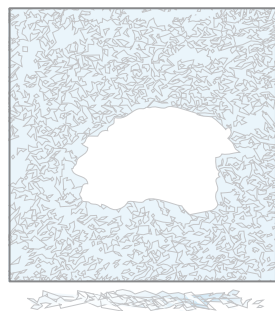

*Break pattern of toughened glass*

### 3.2. Use

Since it breaks into blunt pieces, thermally toughened glass is perfectly suited to all applications where the aim is to prevent injury from sharp splinters of glass in the event of breakage; for example in bus shelters, telephone boxes, shower screens and so forth.

### 3.3. Certification

Thermally toughened glass complies with standard EN 12150. Thermally toughened and heat-soak treated glass complies with standard EN 14179. They are CE-marked in accordance with these standards.

## 4. EUROPEAN CLASSIFICATION STANDARDS

In order to classify and distinguish the performance of various products, new EN European standards have been published by the European Committee for Standardisation (CEN).

These standards are gradually replacing the former national standards such as NBN in Belgium and NF in France (which are now becoming obsolete) and are being recognised as national standards in themselves. As a result, following publication, European standard EN 12543 on laminated glass is now referred to as standard NBN EN 12543 in Belgium, NF EN 12543 in France and so forth. In reality, the text adopted is exactly the same in the various countries.

*NB:* In this brochure, standards are referred to solely by the prefix 'EN' rather than 'NBN EN' or 'NF EN'; the documents are exactly the same, though.

In terms of safety glass, four test and classification standards have been published:

- EN 12600: Glass in building - Pendulum test – Impact test method and classification for flat glass (2002)
- EN 356: Glass in building - Security glazing – Testing and classification of resistance against manual attack (1999)
- EN 1063: Glass in building - Security glazing – Testing and classification of resistance against bullet attack (1999)
- EN 13541: Glass in building - Testing and classification of resistance against explosion pressure (2000).

The four standards are described briefly on the following pages. Details are also given of the corresponding AGC product ranges.

### Use of glass products

To make appropriate use of glass products, the following three points should be borne in mind:

- 1) The European standards mentioned only set out a product's class; they never stipulate how to use a product within a specific project. The choice as to the most suitable glass product to use is one for the national authorities and each country may publish its own rules, which must be observed.
- 2) In all cases, the thicknesses corresponding to a particular class are merely the minimum applicable according to the test carried out; the actual thicknesses to be used should be determined on a case-by-case basis depending on the size of the glass, the stresses upon it and the installation method to be used.
- 3) In all cases, using safety glass is only a viable option if the accompanying joinery provides the same level of resistance since it is naturally the weakest component of a unit which will determine the level of resistance of the assembly as a whole. Test and classification standards are also available for joinery and are similar to those for glass.

## 5. EN 12600 – IMPACT RESISTANCE

### Test principle

Standard EN 12600 'Pendulum test – Impact test method and classification for flat glass' details the classification of glasses according to impact by soft material. The test detailed uses a twin-tyre impactor and is used to classify glass products in terms of risk of injury and defenestration.



Pendulum test EN 12600

The classification makes a distinction between the fall height and the type of breakage.

| Fall height: | Type of breakage:                                                                      |
|--------------|----------------------------------------------------------------------------------------|
| 1: 1200 mm   | A: cracks with separated fragments (annealed, heat-strengthened, chemically toughened) |
| 2: 450 mm    | B: cracks with combined fragments (laminated, wired, film on annealed glass)           |
| 3: 190 mm    | C: disintegration into small particles (thermally toughened)                           |

Performance classification of a glass product is expressed as follows using two figures and one letter:  $\alpha$  ( $\beta$ )  $\phi$  where:

- $\alpha$  is the highest class of drop height during which the glass either breaks or does not break in accordance with one of the two breakage patterns described below;
- $\beta$  is the type of breakage;
- $\phi$  is the highest class of drop height during which the glass either breaks or does not break without allowing penetration (in accordance with the first of the two criteria listed below); where a glass breaks at the lowest fall height allowing penetration, it is demoted as 0.

The two fragmentation methods accepted by the standard for criteria  $\alpha$  are:

- Numerous cracks appear but no shear or opening is allowed within the test piece through which a 76-mm diameter sphere can pass when a maximum force of 25 N is applied
- Disintegration occurs and the 10 largest crack-free particles collected and weighed altogether within three minutes after impact shall weigh no more than a mass equivalent to 6,500 mm<sup>2</sup> of the original test piece.



Pendulum test EN 12600

### Examples

- A laminated glass is classed as **1B1** if it resists an impact from a fall height of **1200 mm** without allowing penetration.
- A laminated glass is classed as **2B2** if it resists an impact from a fall height of **450 mm** without allowing penetration.
- A thermally toughened glass is classed as **1C1** if it resists an impact from a fall height of **1,200 mm** without breaking.

### AGC range – Toughened glass

Toughened and toughened heat-soaked glasses meet the criteria set out in standard EN 12600.

#### Range toughened glass

| Class | Composition | Weight (kg/m <sup>2</sup> ) |
|-------|-------------|-----------------------------|
| 1C3   | 4           | 10.0                        |
| 1C3   | 5           | 12.5                        |
| 1C2   | 6           | 15.0                        |
| 1C2   | 8           | 20.0                        |
| 1C1   | 10          | 25.0                        |
| 1C1   | 12          | 30.0                        |
| 1C1   | 15          | 37.5                        |
| 1C1   | 19          | 47.5                        |

This classification applies to all toughenable glasses (Planibel, Stopsol, Sunergy, Stopray T, etc.) with the exception of Colorbel enamelled and Artlite silk-screen printed glasses, in respect of which no classification is required.

### AGC range – Laminated glass

Stratobel laminated safety glasses and Stratophone acoustic laminated safety glasses are classified as follows in line with standard EN 12600.

#### Range Stratobel - Stratophone

| Class | Composition | Thickness (mm) | Weight (kg/m <sup>2</sup> ) |
|-------|-------------|----------------|-----------------------------|
| 2B2   | 33.1        | 6              | 15.0                        |
| 2B2   | 44.1        | 8              | 20.0                        |
| 1B1   | 55.1        | 10             | 25.0                        |
| 1B1   | 66.1        | 12             | 30.0                        |
| 1B1   | 33.2        | 7              | 16.0                        |
| 1B1   | 44.2        | 9              | 21.0                        |
| 1B1   | 55.2        | 11             | 26.0                        |
| 1B1   | 66.2        | 13             | 31.0                        |


### Notes:

- Thickness compositions in excess of 66.2 (i.e. 88.2, ....) also meet the criteria for class 1B1.
- In some specific cases (sports halls, psychiatric hospitals, etc.), laminated glass with strengthened or toughened components may be appropriate. This product is called Stratobel Super.
- Stratophone acoustic laminated safety glass performs to the same level as Stratobel laminated glass when impacted.


## 6. EN 356 – BURGLAR RESISTANCE

### Test principle

Standard EN 356 «Security glazing – Testing and classification of resistance against manual attack» sets out the testing methods to be used to classify glasses in terms of their resistance to burglary. There are eight classes of increasing resistance; the first five classes denoted P1A to P5A are based on the falling ball test using a metal ball weighing 4.1 kg; the next three classes denoted P6B to P8B are based on an axe test.

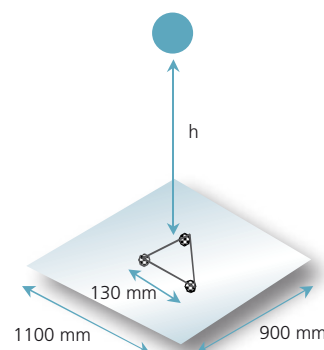

Ball test EN 356

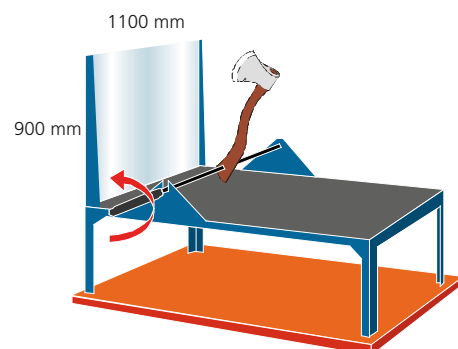

Axe test EN 356

In falling-ball tests, a test sheet measuring 1,100 mm x 900 mm is positioned horizontally and is impacted by a ball weighing 4.1 kg in a triangular area in the centre of the glass (13 cm between impacts). The number of impacts and the drop height vary depending on the class.

### Classification of resistance against vandalism, burglary and theft

| Test | Class | Test description                            |
|------|-------|---------------------------------------------|
| Ball | P1A   | 3 impacts by a ball falling from 1,500 mm   |
|      | P2A   | 3 impacts by a ball falling from 3,000 mm   |
|      | P3A   | 3 impacts by a ball falling from 6,000 mm   |
|      | P4A   | 3 impacts by a ball falling from 9,000 mm   |
|      | P5A   | 3x3 impacts by a ball falling from 9,000 mm |
| Axe  | P6B   | 30 to 50 blows by a hammer and an axe       |
|      | P7B   | 51 to 70 blows by a hammer and an axe       |
|      | P8B   | > 70 blows by a hammer and an axe           |

The ball test is considered successful if the ball does not pass through the test sheet entirely within five seconds of the moment of impact.

In the axe test, a test sheet measuring 1,100 mm x 900 mm is positioned vertically. First the different test-sheet glasses are broken using hammer blows (minimum of 12). Next, axe blows are used to try to make a hole in the centre of the glass.

The axe test is considered successful if the area (400 mm x 400 mm) subject to the axe blow does not become completely detached from the rest of the test sheet.

### AGC range

AGC has a range of Stratobel (and Stratophone) glasses which meet the criteria for the different classes within standard EN 356.

#### Range Stratobel and Stratophone

| Class     | Product         | Composition     | Thickness (mm) | Weight (kg/m <sup>2</sup> ) |
|-----------|-----------------|-----------------|----------------|-----------------------------|
| P1A - P2A | Stratobel 701-1 | 33.2            | 7              | 16                          |
| P1A - P2A | Stratobel 901-2 | 44.2            | 9              | 21                          |
| P3A - P4A | Stratobel 801-1 | 33.4            | 8              | 17                          |
| P3A - P4A | Stratobel 002-1 | 44.4            | 10             | 22                          |
| P5A       | Stratobel 002-1 | 44.6            | 10             | 22                          |
| P5A       | Stratobel 402-3 | 66.6            | 14             | 33                          |
| P6B       | Stratobel 502-1 | multi-laminated | 15             | 33                          |
| P6B       | Stratobel 505-2 | bi-laminated    | 15             | 33                          |
| P6B       | Stratobel 802-2 | multi-laminated | 18             | 43                          |
| P7B       | Stratobel 303-3 | multi-laminated | 23             | 53                          |
| P8B       | Stratobel 504-4 | multi-laminated | 35             | 81                          |
| P8B       | Stratobel 803-5 | multi-laminated | 28             | 64                          |
| P8B       | Stratobel 905-8 | multi-laminated | 49             | 114                         |

**NB:** For safety reasons, high-performance compositions are coded.

A Stratobel PC range of laminated glasses incorporating polycarbonate components is also available; these glasses are thinner and lighter but provide the same level of performance.

#### Range Stratobel PC (Polycarbonate)

| Class | Product              | Thickness (mm) | Weight (kg/m <sup>2</sup> ) |
|-------|----------------------|----------------|-----------------------------|
| P6B   | Stratobel PC 214.541 | 15             | 28                          |
| P7B   | Stratobel PC 216.541 | 17             | 30                          |
| P8B   | Stratobel PC 219.841 | 20             | 34                          |

## 7. EN 1063 – BULLET RESISTANCE

### Test principle


Standard EN 1063 «Security glazing – Testing and classification of resistance against bullet attack» describes the methods to be used to classify bullet-resistant glass.

The standard makes a distinction between resistance against two types of weapon: handguns and rifles (BR classes) and shotguns (SG classes).

There are nine classes. For each category of weapon tested, the glass is classed as bullet-resistant if it stops all the bullets on the three sheets tested. The report also states whether or not there are any splinters – (S) or (NS) – behind the glazing.

Classes BR1 to BR7 contain glasses offering increasing levels of protection. This means that a glass meeting the requirements stipulated for a given class also meet those of the classes below it. There is no correlation between SG and BR classes.

*Note:* In addition to the classes stipulated in the standard, the range also includes a composition offering resistance to Kalashnikov AK47s.

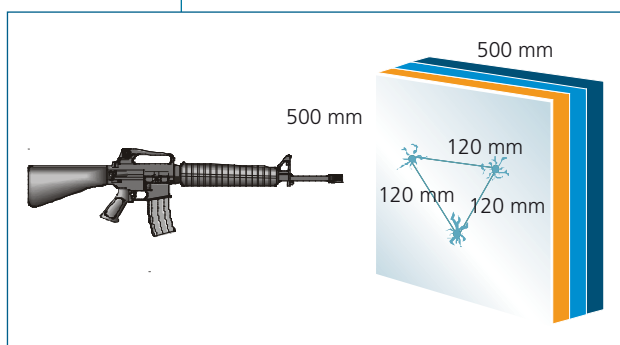

test of bullet-proof -  
Class EN 1063



BR1 BR2 BR3 BR4 BR5 BR6 BR7 SG Kalash

### Classification of resistance against firearm attacks - Class EN 1063

|                                      |                |                  |                          |                                                              | Test conditions |                       |                   |                        |
|--------------------------------------|----------------|------------------|--------------------------|--------------------------------------------------------------|-----------------|-----------------------|-------------------|------------------------|
| Class                                | Type of weapon | Calibre          | Type of ammunition       | Mass of ammunition (g)                                       | Range (m)       | Bullet velocity (m/s) | Number of strikes | Striking distance (mm) |
| BR1                                  | Rifle          | 0,22 Long rifle  | L/RN                     | 2,6 ± 0,1                                                    | 10,00 ± 0,5     | 360 ± 10              | 3                 | 120 ± 10               |
| BR2                                  | Handgun        | 9 mm Lugar       | FJ <sup>1</sup> /RN/SC   | 8,0 ± 0,1                                                    | 5,00 ± 0,5      | 400 ± 10              | 3                 | 120 ± 10               |
| BR3                                  | Handgun        | 0,357 Magnum     | FJ <sup>1</sup> /CB/SC   | 10,2 ± 0,1                                                   | 5,00 ± 0,5      | 430 ± 10              | 3                 | 120 ± 10               |
| BR4                                  | Handgun        | 0,44 Rem. Magnum | FJ <sup>2</sup> /FN/SC   | 15,6 ± 0,1                                                   | 5,00 ± 0,5      | 440 ± 10              | 3                 | 120 ± 10               |
| BR5                                  | Rifle          | 5,56 x 45 *      | FJ <sup>2</sup> /PB/SCP1 | 4,0 ± 0,1                                                    | 10,00 ± 0,5     | 950 ± 10              | 3                 | 120 ± 10               |
| BR6                                  | Rifle          | 7,62 x 51        | FJ <sup>1</sup> /PB/SC   | 9,5 ± 0,1                                                    | 10,00 ± 0,5     | 830 ± 10              | 3                 | 120 ± 10               |
| BR7                                  | Rifle          | 7,62 x 51 **     | FJ <sup>2</sup> /PB/HC1  | 9,8 ± 0,1                                                    | 10,00 ± 0,5     | 820 ± 10              | 3                 | 120 ± 10               |
|                                      |                |                  |                          |                                                              |                 |                       |                   |                        |
| SG1                                  | Shotgun        | Cal 12/70        | Solid lead <sup>3</sup>  | 31,0 ± 0,5                                                   | 10,00 ± 0,5     | 420 ± 20              | 1                 | -                      |
| SG2                                  |                | Cal 12/70        | Solid lead <sup>3</sup>  | 31,0 ± 0,5                                                   | 10,00 ± 0,5     | 420 ± 20              | 3                 | 120 ± 10               |
| * twist length 178 mm approx. 10 mm  |                |                  | FJ                       | Full metal jacket                                            |                 |                       |                   |                        |
| ** twist length 254 mm approx. 10 mm |                |                  | FN                       | Flat nose bullet                                             |                 |                       |                   |                        |
| 1 Plated steel jacket                |                |                  | HC1                      | Steel hard core, mass 3.7 g approx. 0.1 g, hardness > 63 HRC |                 |                       |                   |                        |
| 2 Brass alloy jacket                 |                |                  | PB                       | Pointed bullet                                               |                 |                       |                   |                        |
| 3 Brenneke slug                      |                |                  | RN                       | Round nose bullet                                            |                 |                       |                   |                        |
| L Lead                               |                |                  | SC                       | Soft core (with lead)                                        |                 |                       |                   |                        |
| CB Coned bullet                      |                |                  | SCP1                     | Soft core (with lead) and steel penetrator (type SS109)      |                 |                       |                   |                        |

### AGC range

AGC offers a range of Stratobel glasses which meet the criteria for the different classes within standard EN 1063. For the highest classes, to reduce the thickness of laminated glasses, AGC has also developed a range of double-glazing solutions combining two panes of laminated Stratobel to achieve the desired level of performance.

#### Range Stratobel


| Class       | Product          | Thickness (mm) | Weight (kg/m <sup>2</sup> ) |
|-------------|------------------|----------------|-----------------------------|
| BR1 - S     | Stratobel 402-1  | 14             | 32                          |
| BR1 - NS    | Stratobel 802-5  | 18             | 42                          |
| BR2 - S     | Stratobel 003-1  | 20             | 47                          |
| BR2 - NS    | Stratobel 104-1  | 31             | 73                          |
| BR3 - S     | Stratobel 603-1  | 26             | 63                          |
| BR3 - NS    | Stratobel 704-3  | 37             | 89                          |
| BR4 - S     | Stratobel 304-6  | 33             | 80                          |
| BR4 - NS    | Stratobel 1207-1 | 61             | 125                         |
| BR5 - S     | Stratobel 504-4  | 35             | 81                          |
| BR5 - NS    | Stratobel 806-2  | 58             | 141                         |
|             | Stratobel 4207-1 | 64             | 127                         |
| BR6 - S     | Stratobel 1207-1 | 61             | 125                         |
| BR6 - NS    | Stratobel 408-1  | 74             | 179                         |
|             | Stratobel 3209-1 | 83             | 176                         |
| BR7 - S     | Stratobel 6208-1 | 76             | 157                         |
| BR7 - NS    | Stratobel 009-1  | 80             | 188                         |
|             | Stratobel 8209-1 | 88             | 188                         |
|             | Stratobel 304-6  | 33             | 76                          |
| SG1 - S     | Stratobel 9207-1 | 69             | 145                         |
| SG2 - S     | Stratobel 504-4  | 35             | 81                          |
| SG2 - NS    | Stratobel 9208-1 | 79             | 162                         |
| Kalashnikov | Stratobel 504-4  | 35             | 81                          |

*NB:*

*For safety reasons, the configurations are coded.*

*The four-digit codes refer to monolithic laminated glass;  
the five-digit codes refer to laminated glass used in an insulating glazing assembly.*

A Stratobel PC range of laminated glasses incorporating polycarbonate components is also available; there is never any splintering on the protected side (NS) of these glasses and they are thinner and lighter but provide the same level of performance.

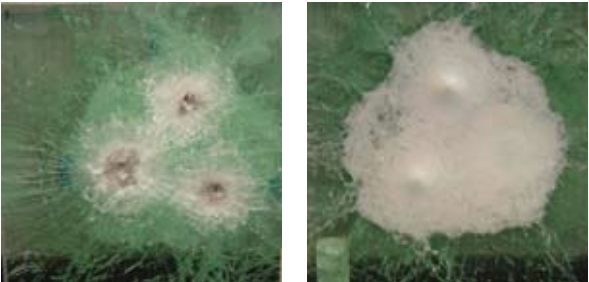

The pictures opposite show a test sheet of Stratobel PC following a test. Note the three impact points of the bullet on the front of the glass and the corresponding indentations to the polycarbonate on the back.

Range Stratobel PC (Polycarbonate)

| Class    | Product              | Thickness (mm) | Weight (kg/m²) |
|----------|----------------------|----------------|----------------|
| BR1 - NS | Stratobel PC 810.061 | 11             | 20             |
| BR2 - NS | Stratobel PC 815.051 | 15             | 31             |
| BR3 - NS | Stratobel PC 819.070 | 19             | 41             |
| BR4 - NS | Stratobel PC 823.860 | 24             | 51             |
| BR5 - NS | Stratobel PC 835.800 | 36             | 81             |
| BR6 - NS | Stratobel PC 841.370 | 42             | 93             |
|          | Stratobel PC 848i560 | 49             | 82             |
| BR7 - NS | Stratobel PC 889.600 | 90             | 210            |
|          | Stratobel PC 890i100 | 90             | 185            |
|          |                      |                |                |
| SG1 - NS | Stratobel PC 823.860 | 24             | 52             |
| SG2 - NS | Stratobel PC 835.800 | 36             | 81             |

NB:  
For safety reasons, the configurations are coded.  
Codes with an 'i' indicate laminated glass in an insulating-glazing assembly.

8. NATIONAL REGULATIONS AND SAFETY-GLASS APPLICATIONS

8.1. Safety-glass applications

The European standards detailed above set out the classification system for safety glass; they do not specify how a given type of glass should be used depending on its application or location. This is the responsibility of national authorities and standards concerning applications should be published to provide such information.

Where no national regulations exist, the table on pages 16 and 17 give some general information regarding the choice of the appropriate laminated glass depending on its application and the risks it is designed to prevent.

8.2. National regulations

Some countries have published nationally applicable documents and/or standards pertaining to the use of safety glass, at least in terms of accident prevention and protection against falling. For example:

- NBN S 23-002 (STS 38): 2007 in Belgium
- NEN 3569 in The Netherlands
- UNI 7697 In Italy
- others



|                                           | Purpose                                                                                                                                                                                                                                                                                                                                                                                                                                                                                         | Corresponding classification          |  | Recommended solutions                                                                                                                                                                                                                                                                                                                                                                | Sample applications                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                      |
|-------------------------------------------|-------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|---------------------------------------|--|--------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|
| Protection of individuals<br>EN 12600     | <b>Accident prevention</b><br>To prevent the risk of cuts and serious injury due to accidental impact against a glass surface or to sharp splinters. Due to their breakage patterns, both toughened glass and laminated Stratobel glass protect against sharp pieces of glass.                                                                                                                                                                                                                  | 1C1 – 1C2 - ...<br><br>2B2 – 1B1      |  | Toughened glass<br><br><br>2 panes of glass and 1 PVB min.                                                                                                                                                                                                                                        | Ideal for glass in doors, windows (where there is no risk of falling), shower screens, bus shelters, roof glazing and so forth.                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                          |
|                                           | <b>Protection against falling (defenestration)</b><br>Where glass surfaces face directly onto an empty space, to prevent individuals falling through the glass, even if it breaks by accident.                                                                                                                                                                                                                                                                                                  | 1B1                                   |  | 2 panes of glass and 2 PVB min.<br>                                                                                                                                                                                                                                                               | Balcony railings, banisters, spandrels, balustrades, internal partitions, lift partitions, façade glazing to ground level and so forth.                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                  |
| Protection of property<br>EN 356          | <b>Protection against vandalism and burglary</b><br>Basic-level protection: protection against acts of vandalism, throwing of stones, and so forth.<br><br>Mid-level protection: protection against petty crime.<br><br>Enhanced protection: protection against premeditated attacks by perpetrators with limited time, the aim being to dissuade them from breaking in and stealing items; even if cracked, the glass remains in place and continues to act as a barrier until it is replaced. | P1A – P2A<br><br>P3A – P4A<br><br>P5A |  | 2 panes of glass and 2 PVB min.<br><br><br>2 panes of glass and 4 PVB min.<br><br><br>2 panes of glass and 6 PVB min.<br> | For private ground-floor residences, commercial office blocks, shop windows, glazing in public buildings and so on and on urban sites, close to stadiums and event locations. May also be used for floors and roofs in villas and apartments.<br><br>For isolated private residences and for ground-floor commercial office blocks in general.<br><br>For isolated dwellings in at-risk areas and second homes, at-risk commercial buildings such as pharmacies and specialist shops selling hi-fi and video systems, computers, electrical appliances and/or tobacco/cigarettes, as well as fashion boutiques and shops selling fine leather goods, sports items, perfume and so forth. |
|                                           | <b>Protection against organised theft</b><br>In the event of repeated and premeditated manual attack by perpetrators with a larger array of weapons, Stratobel can delay and prevent a break-in and the theft of goods; even if cracked, the glass remains in place and continues to act as a barrier until it is replaced.                                                                                                                                                                     | P6B – P8B                             |  | Multilaminated or Stratobel PC<br>                                                                                                                                                                                                                                                              | Recommended for high-risk shop windows such as jewellers, businesses selling art and antiquities, embassies, prisons, museum display cases and so on.                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                    |
| Protection against firearms<br>EN 1063    | <b>Bullet resistance</b><br>Stratobel provides effective protection against different types of firearm. The appropriate structure should be selected on a case-by-case basis depending on the risks encountered.                                                                                                                                                                                                                                                                                | BR1 to BR7<br><br>SG1 to SG2          |  | Multilaminated or Stratobel PC<br>                                                                                                                                                                                                                                                              | Recommended for counters and glazing in banks, financial establishments, post offices and foreign exchange booths, embassies, vehicles transporting money and so on.                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                     |
| Protection against explosions<br>EN 13541 | <b>Explosion resistance</b><br>Stratobel provides effective protection against explosions. The appropriate structure should be selected on a case-by-case basis depending on the risks encountered.                                                                                                                                                                                                                                                                                             | Consult AGC                           |  | Tailor-made configuration                                                                                                                                                                                                                                                                                                                                                            | Recommended to protect buildings in the event of an external explosion, for example in the pharmaceutical, chemical and petrochemical industries, banks, embassies and so on.                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                            |

## 9. AVAILABILITY

The availability as well as the possible thickness and size of toughened and laminated glasses will vary by market. For further details, please visit [www.yourglass.com](http://www.yourglass.com) or contact us.

## 10. INSTALLATION INSTRUCTIONS

Without going into great detail, three key points should be borne in mind when installing Stratobel laminated glass:

- no water should be left trapped in the rebates;
- setting blocks should be inserted correctly;
- waterproofing materials used should be compatible with the PVB (and any coatings included in the laminated assembly). It is the responsibility of the individuals installing the waterproofing products to check that they are compatible.

Non-symmetrical laminated glasses (resistance against burglary or firearms) and/or double-glazing units including one or more laminated glasses must be installed facing in the correct direction to ensure the desired performance.

Strict rules must also be observed when fitting glass in floors and stairs.

For further details, please consult our «Installation instructions» brochures, which are available upon request or by visiting [www.yourglass.com](http://www.yourglass.com).

NB: In all cases, the thicknesses corresponding to a particular class are merely the minimum applicable according to the test carried out; the actual thicknesses to be used should be determined on a case-by-case basis depending on the size of the glass, the stresses upon it and the installation method to be used.

## 11. MAINTENANCE, STORAGE, HANDLING AND PROCESSING

Detailed brochures are available on precautions to be taken when storing, handling and processing Stratobel laminated glass and, more specifically, where the composition includes a coated glass.

AUSTRIA - Zimmermann Bauglas  
Tel: +43 262 271 960 - Fax: +43 262 271 964  
[wzi@glasagentur-zimmermann.at](mailto:wzi@glasagentur-zimmermann.at)

BELGIUM - AGC Flat Glass Europe  
Tel: +32 (0)2 674 31 11 - Fax: +32 (0)2 672 44 62  
[sales.belux@eu.agc-flatglass.com](mailto:sales.belux@eu.agc-flatglass.com)

BULGARIA - AGC Flat Glass Bulgaria  
Tel: +359 2 9555 387 - Fax: +359 2 8500 256  
[sales.bulgaria@eu.agc-flatglass.com](mailto:sales.bulgaria@eu.agc-flatglass.com)

CROATIA/SLOVENIA/BOSNIA & HERZEGOVINA -  
AGC Flat Glass Adriatic  
Tel: +385 1 6117 942 - Fax: +385 1 6117 943  
[sales.adriatic@eu.agc-flatglass.com](mailto:sales.adriatic@eu.agc-flatglass.com)

CZECH REPUBLIC - AGC Flat Glass Czech  
Tel: +420 417 50 11 11 - Fax: +420 417 502 121  
[sales.czech@eu.agc-flatglass.com](mailto:sales.czech@eu.agc-flatglass.com)

DENMARK - AGC Flat Glass Denmark  
Tel: +45 33 91 12 23 - Fax: +45 33 91 20 04  
[sales.denmark@eu.agc-flatglass.com](mailto:sales.denmark@eu.agc-flatglass.com)

ESTONIA - AGC Flat Glass Baltic  
Tel: +371 6 7139 359 - Fax: +371 6 7139 549  
[sales.estonia@eu.agc-flatglass.com](mailto:sales.estonia@eu.agc-flatglass.com)

FINLAND - AGC Flat Glass Suomi  
Tel: +358 9 43 66 310 - Fax: +358 9 43 66 3111  
[sales.suomi@eu.agc-flatglass.com](mailto:sales.suomi@eu.agc-flatglass.com)

FRANCE - AGC Flat Glass France  
Tel: +33 (0)1 57 58 31 54 - Fax: +33 (0)1 57 58 31 63  
[sales.france@eu.agc-flatglass.com](mailto:sales.france@eu.agc-flatglass.com)

GERMANY - Bluhm & Plate  
Tel: +49 (0)40 670 88 40 - Fax: +49 (0)40 670 88 410  
[info@bluhm.de](mailto:info@bluhm.de)

GERMANY - Clemens Schlatt  
Tel: +49 (0)2871 9 94 00 - Fax: +49 (0)2871 18 36 81  
[sales.schlatt@eu.agc-flatglass.com](mailto:sales.schlatt@eu.agc-flatglass.com)

GREECE - AGC Flat Glass Hellas  
Tel: +30 210 666 6011 - Fax: +30 210 666 9732  
[sales.hellas@eu.agc-flatglass.com](mailto:sales.hellas@eu.agc-flatglass.com)

HUNGARY - AGC Flat Glass Hungary  
Tel: +36 1 219 51 87 - Fax: +36 1 215 54 42  
[sales.hungary@eu.agc-flatglass.com](mailto:sales.hungary@eu.agc-flatglass.com)

ITALY - AGC Flat Glass Italia  
Tel: +390 2626 90 110 - Fax: +390 2657 01 01  
[sales.italia@eu.agc-flatglass.com](mailto:sales.italia@eu.agc-flatglass.com)

LATVIA - AGC Flat Glass Baltic  
Tel: +371 6 713 93 59 - Fax: +371 6 713 95 49  
[sales.latvia@eu.agc-flatglass.com](mailto:sales.latvia@eu.agc-flatglass.com)

LITHUANIA - AGC Flat Glass Baltic  
Tel: +371 6 7139 360 - Fax: +371 6 7139 550  
[sales.lithuania@eu.agc-flatglass.com](mailto:sales.lithuania@eu.agc-flatglass.com)

NETHERLANDS - AGC Flat Glass Nederland  
Tel: +31 (0)344 67 9922 - Fax: +31 (0)344 67 97 24  
[sales.nederland@eu.agc-flatglass.com](mailto:sales.nederland@eu.agc-flatglass.com)

POLAND - AGC Flat Glass Polska  
Tel: +48 22 872 0223 - Fax: +48 22 872 9760  
[sales.polska@eu.agc-flatglass.com](mailto:sales.polska@eu.agc-flatglass.com)

ROMANIA - AGC Flat Glass Romania  
Tel: +40 264 40 60 17 - Fax: +40 264 440 558  
[sales.romania@eu.agc-flatglass.com](mailto:sales.romania@eu.agc-flatglass.com)

RUSSIA - AGC Flat Glass Rus  
Tel: +7 (095) 411 65 65 - Fax: +7 (095) 411 65 64  
[sales.russia@eu.agc-flatglass.com](mailto:sales.russia@eu.agc-flatglass.com)

SERBIA-MONTENEGRO - AGC Flat Glass Jug  
Tel: +381 11 30 96 232 - Fax: +381 11 30 96 232  
[sales.jug@eu.agc-flatglass.com](mailto:sales.jug@eu.agc-flatglass.com)

SPAIN & PORTUGAL - AGC Flat Glass Ibérica  
Tel: +34 934 670 760 - Fax: +34 934 670 770  
[sales.iberica@eu.agc-flatglass.com](mailto:sales.iberica@eu.agc-flatglass.com)

SWEDEN & NORWAY - AGC Flat Glass Svenska  
Tel: +46 8 768 40 80 - Fax: +46 8 768 40 81  
[sales.svenska@eu.agc-flatglass.com](mailto:sales.svenska@eu.agc-flatglass.com)

SWITZERLAND - AGC Flat Glass Europe  
Tel: +41 32 753 71 33 - Fax: +41 32 753 61 78  
[sales.switzerland@eu.agc-flatglass.com](mailto:sales.switzerland@eu.agc-flatglass.com)

UKRAINE - AGC Flat Glass Ukraine  
Tel: +38 0442 362 068 - Fax: +38 0445 012 144  
[sales.ukraine@eu.agc-flatglass.com](mailto:sales.ukraine@eu.agc-flatglass.com)

UNITED KINGDOM - AGC Flat Glass UK  
Tel: +44 1788 53 53 53 - Fax: +44 1788 56 08 53  
[sales.uk@eu.agc-flatglass.com](mailto:sales.uk@eu.agc-flatglass.com)

OTHER COUNTRIES - AGC Flat Glass Europe  
Tel: +32 (0)2 674 31 11 - Fax: +32 (0)2 672 44 62  
[sales.headquarters@eu.agc-flatglass.com](mailto:sales.headquarters@eu.agc-flatglass.com)

**AGC**

GLASS UNLIMITED

[www.yourglass.com](http://www.yourglass.com)